

DATA SHEET



**LATROBE SPECIALTY
STEEL COMPANY**

Latrobe, PA 15650-0031 USA

Issue 1

Crucible Industries CPM[®] 20CV Powder Metal Stainless Tool Steel

LATROBE SPECIALTY STEEL your source for all Crucible CPM products

Typical Composition

C	Mn	Si	Cr	W	Mo	V
1.90	0.30	0.30	20.00	0.60	1.00	4.00


CPM 20CV is a highly wear resistant, powder metallurgy stainless tool steel. The steel contains a large volume of extremely hard vanadium carbides, which provide excellent wear resistance. CPM 20CV contains the highest amount of chromium of any high-vanadium stainless steel currently available. The chromium-rich matrix provides outstanding corrosion resistance.

CPM 20CV is a versatile stainless tool steel with a unique combination of high wear resistance, high corrosion resistance, good impact toughness, and excellent polishability.

This combination of properties is the result of the fine grain size, small carbides, and superior cleanliness of the powder metallurgy (PM) microstructure.

CPM 20CV excels in applications, which require a combination of high wear resistance and high corrosion resistance. The unique combination of properties makes CPM 20CV an excellent steel for plastic injection feed screws, barrel liners, screw tips, and mold cavities, especially for plastic resins which contain abrasive fillers. Other applications include food processing equipment, pelletizer knives, granulator knives, and high-performance custom knives.

Relative Properties

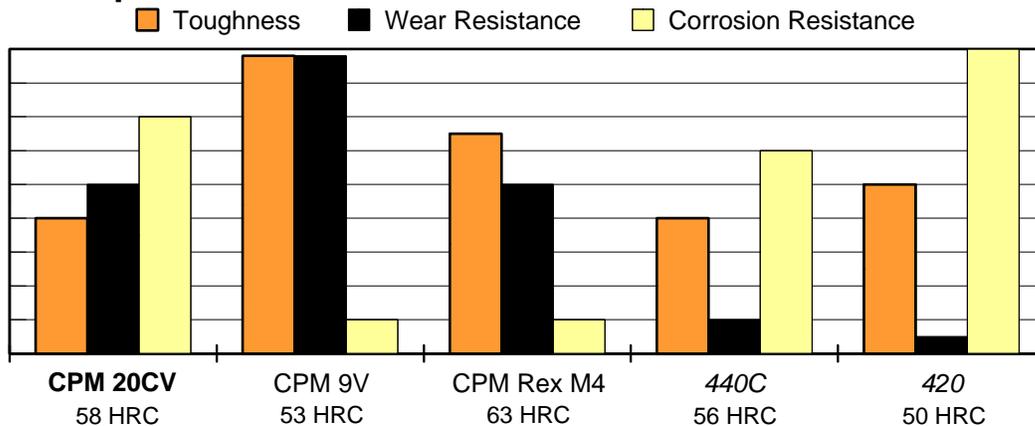

Physical Properties

Density: 0.275 lb/in³ (7616 kg/m³)

Modulus of Elasticity: 31x10⁶ psi (214 GPa)

Coefficient of Thermal Expansion:

Temperature °F	in/in/°F x 10 ⁻⁶	Temperature °C	mm/mm/°C x 10 ⁻⁶
68 - 212	6.06	20 - 100	10.9
68 - 392	6.23	20 - 200	11.2
68 - 572	6.56	20 - 300	11.8
68 - 752	6.73	20 - 400	12.1
68 - 932	6.84	20 - 500	12.3

Machinability: 35-40% of a 1% carbon steel

Edge Retention (CATRA Test Relative to 440C)

GRADE	%
CPM 20CV	180
14-2-4 CrMoV	145
14-4 CrMo	120
440C	100

The CATRA (Cutlery & Allied Trade Research Association) test machine measures the total number of silica impregnated cards cut in a sequence of passes along a blade. It is considered a relative measure of edge retention and wear resistance.

CPM® 20CV

HEAT TREATING INSTRUCTIONS

(See Tech-Topics Bulletin 102 for a more thorough explanation of heat treating.)

HARDENING:

Preheating: Heat to 1400-1450°F (760-788°C) and equalize.

Austenitizing (High Heat): Heat rapidly from the preheat to a temperature to within 1960-2150°F (1071-1177°C). A lower austenitizing temperature will maximize impact toughness. A higher austenitizing temperature will maximize wear resistance and corrosion resistance. Soak at the austenitizing temperature for 30 minutes.

Quenching Pressurized gas or warm oil.

For pressurized gas, the furnace should have a minimum quench pressure of 4 bars. A quench rate of approximately 400 °F (222°C) per minute to below 1000°F (538°C) is critical to obtain the desired properties.

For oil, quench until black, about 900°F (482°C), then cool in still air to 150-125°F (66-51°C).

Cryogenic Treatment: For austenitizing at 2100°F (1149°C) or higher, a cryogenic treatment is recommended after quenching to 150 to 125°F (66-51°C) to reduce retained austenite. Cool to -100°F (-73°C), remove from the cooling medium, and allow part to warm to ambient temperature in still air.

Tempering: Temper immediately after quenching, or after quenching and cryogenic treatment.


Typical temperature range is 400-800°F (204-427°C). Hold at temperature for 1 hour per inch (25.4mm) of thickness, 2 hours minimum, then air cool to ambient temperature. The typical service hardness is 56-59 HRC, although higher hardnesses may be used for increased wear resistance. Tempering between 800 and 1100°F (427 to 583°C) will decrease corrosion resistance and toughness.

ANNEALING: Annealing must be performed after hot working and before rehardening.


Heat at a rate not exceeding 400°F per hour (222°C per hour) to 1860-1900°F (1016-1038°C), and hold at temperature for 1 hour per inch (25.4 mm) of maximum thickness; 2 hours minimum. Then cool slowly with the furnace at a rate not exceeding 30°F per hour (15°C per hour) to 1000°F (538°C). Continue cooling to ambient temperature in the furnace or in air. The resultant hardness should be approximately 30 HRC or lower.

HEAT TREATMENT RESPONSE

For Furnace or Salt Bath Hardening:

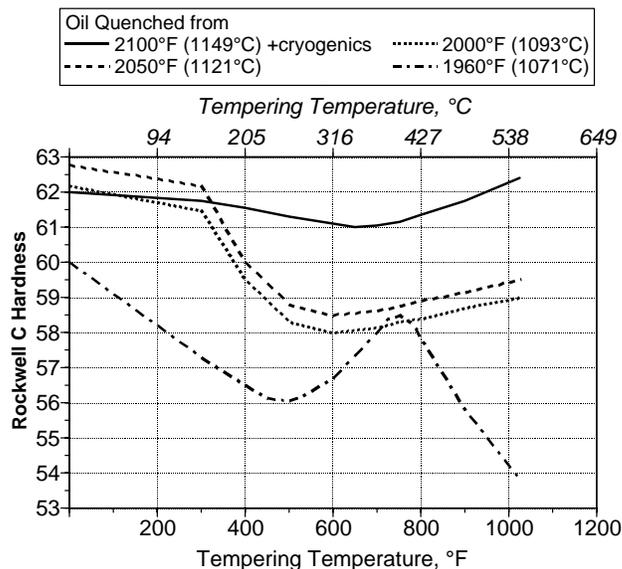

For Vacuum Furnace Hardening:

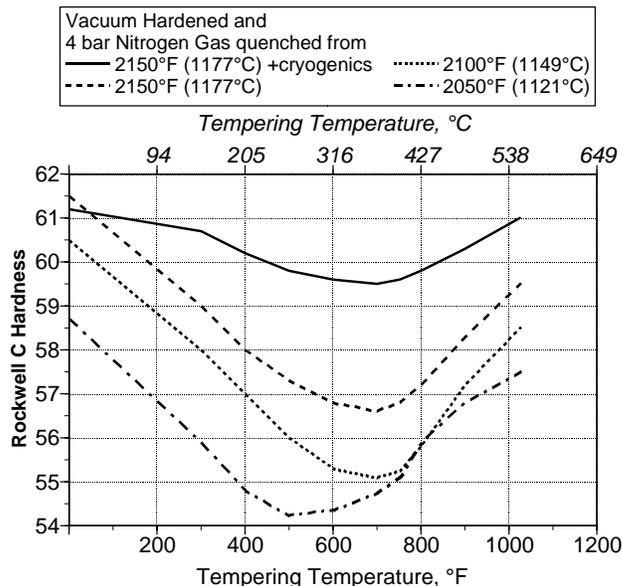

**LATROBE SPECIALTY
STEEL COMPANY**



**Crucible
Industries**

The data presented herein are typical values, and do not warrant suitability for any specific application or use of this material. Normal variations in the chemical composition, the size of the product, and heat treatment parameters may result in different values for the various physical and mechanical properties.

Latrobe, PA Phone: 724-537-7711
FAX: 724-532-6316

Vienna, OH Phone: 800-321-6446
FAX: 330-609-2054

Marlborough, MA Phone: 800-444-4447
FAX: 508-481-6581

WEB: www.latrobesteel.com